

## Experimental and computational study of levofloxacin as corrosion inhibitor for carbon steel in acidic media

**M. E. Ikpi, F. E. Abeng\*, B. O. Okonkwo**

Corrosion and Electrochemistry Research Laboratory,  
Department of Pure and Applied Chemistry, University of Calabar, P.M.B. 1115, Calabar, Nigeria

\*E-mail address: [fidelisabeng@yahoo.com](mailto:fidelisabeng@yahoo.com)

\*Tel: +2348035664813

### ABSTRACT

The corrosion inhibition behaviour of levofloxacin was investigated on carbon steel by means of a 2 M HCl solution, using potentiodynamic polarization measurement and Quantum chemical studies. The inhibitive effect of the studied compound was found to increase with increasing concentration and to increase with increasing temperature. The study reveals that levofloxacin is a mixed-type corrosion inhibitor. The adsorption of levofloxacin on carbon steel surface obeys the Langmuir adsorption isotherm and involves physical adsorption mechanisms. Quantum chemical studies corroborate experimental results.

**Keywords:** Corrosion Inhibition, Polarization, levofloxacin and Adsorption

### 1. INTRODUCTION

Corrosion is a naturally occurring phenomenon commonly defined as the deterioration of material by chemical interaction with their environment. Corrosion of metals has caused huge economic losses involving billions of dollars each year in many industries. The international measure of prevention, application and economic of corrosion technology (IMPACT) estimated the global cost of corrosion to be \$2.5 trillion which is equivalent to 3.4% of Gross Domestic Product GDP (Gerhard, 2001). The IMPACT found that the

introduction of corrosion prevention could result in global saving between 15-35% of the cost damage. Therefore control measures or procedures need to be implemented in order to reduce or inhibit corrosion thereby prolonging the life span of metals. Several approaches have been suggested and implemented to protect metal against corrosion. One of the approaches is using a corrosion inhibitor which is one of the best methods of controlling corrosion. Most of the corrosion inhibitors used are toxic, expensive and difficult to come by. Thus researchers have focused on the use of eco-friendly compounds, that could be obtained conveniently and contain electronegative atoms such as Nitrogen, Sulfur, and Oxygen in the relatively long carbon chain compounds.

Presently a few non-toxic organic compounds such as Azithromycin, Abdullatef (2015); Amoxicillin (Siaka *et al.*, 2013); Cefixime, (Naqvi, *et al.*, 2011); Ciprofloxacin (Akpan and Offiong, 2014a); Amoldipine (Akpan and Offiong, 2014b) have been reported as corrosion inhibitor. Nonetheless, there is still need for research on other organic compounds to be used as inhibitors for industrial application. The objective of this study is to investigate the inhibitory action of Levofloxacin as corrosion inhibitor for a carbon steel in 2 M HCl solution using Potentiodynamic Polarization and Computational methods (<sup>11,12</sup>Rokosz, *et al.*, 2016).


## 2. EXPERIMENTAL DETAILS

### 2. 1. Inhibitor

Levofloxacin is an antibiotic drug under the class of fluoroquinolones. It however has ordered a medicinal value.

The IUPAC nomenclature of the drug is 9-fluoro-2,3-dihydro-3-methyl-10-(4-methyl piperazin-1-yl)-7-oxo-7H-Pyrido(12,3-di)-1,4-benzoxazine-6-carboxylic acid.

With molecular formula  $C_{18}H_{20}FN_3O_4$  and molecular weight of 361.368 g/mol, it has the chemical structure as shown below, in **Figure 1**.

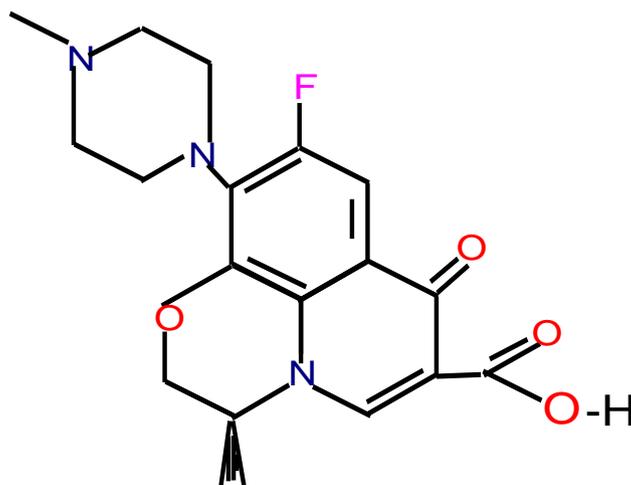

Levofloxacin

**Figure 1.** Chemical structure of Levofloxacin drug

The Tablet of Levofloxacin was obtained from peace Land Pharmaceutical shop Ndidem Usang Iso Road, Calabar-Nigeria, sold under the trade name “Levaquin”. Different concentrations of the drug were prepared by dissolving appropriate quantities of the Tablet from the mass of the drug sample (Akpan and Offiong, 2014).

## 2. 2. Corrosion medium

The corrosive solution of 2 M HCl was prepared from reagent grade of HCl by dilution using doubly distilled water. The concentration of the solution ranges from 50 ppm to 500 ppm.

## 2. 3. Carbon Steel Specimen

A carbon steel with 98% of Fe was used for the investigation, and this was obtained from cylindrical pipeline which was mechanically press cut into square coupons of about 1 cm × 1 cm and used in the electrochemical experiment as the working electrode. The coupons were used after polishing with emery papers. They were degreased in acetone, washed with distilled water, and finally dried.

## 2. 4. Electrochemical Experiment

Potentiodynamic Polarization experiment was carried out using a conventional three-electrode electrochemical cell assembly. Freshly polished carbon steel specimen with an exposed surface area of 1 cm<sup>2</sup> was used as a working electrode, and Saturated Calomel Electrode (SCE), as a reference electrode. The measurements were performed using Gamry Electrochemical Analyzer at 303 K and 323 K. Potentiodynamic current-potential curves were recorded by changing the electrode potential  $E_{\text{corr}}$  automatically with a scan rate of 0.5 mV·s<sup>-1</sup> from a low potential -0.25 to + 0.6 V. Before each run the working electrode was immersed in the test solution for 30 minutes to obtain a steady state. The corrosion rate of the metal was calculated through corrosion current density  $I_{\text{corr}}$ . The linear Tafel segment of anodic and cathodic curves obtained were extrapolated. The inhibition efficiency  $IE\%$  was evaluated from the measured  $I_{\text{corr}}$  values (Ameh *et al.*, 2016; Kumar *et al.*, 2016; Bhawsar *et al.*, 2015).

$$IE\% = \frac{I_{\text{ocorr}} - I_{\text{corr}}}{I_{\text{ocorr}}} \times 100 \quad 1$$

where:  $I_{\text{ocorr}}$  = Blank current density, and  $I_{\text{corr}}$  = Blank + inhibitor.

## 2. 5. Computational Details


### *Quantum Chemical Calculation details*

Quantum chemical calculations were carried out with the aid of Gaussian 03 software suit. The structure of levofloxacin was used as the representative structure for computational studies. The initial structures were refined with self consistent field theory (SCF). The Optimized structures obtained from SCF calculations were later optimized by Density Functional Theory DFT which involve the Becke’s three-parameter hybride functional and Lee-Yang-Paar Correlation functional (B3LYP). Quantum chemical parameters which include the energy of highest occupied molecular orbital ( $E_{\text{HOMO}}$ ), the energy of the lowest


unoccupied molecular orbital ( $E_{LUMO}$ ), the energy  $G_{ab}$  ( $\Delta E = E_{LUMO} - E_{HOMO}$ ) and dipole moment  $\mu$  were recorded.

### 3. RESULTS AND DISCUSSIONS

#### 3. 1. Potentiodynamic Polarization Measurements

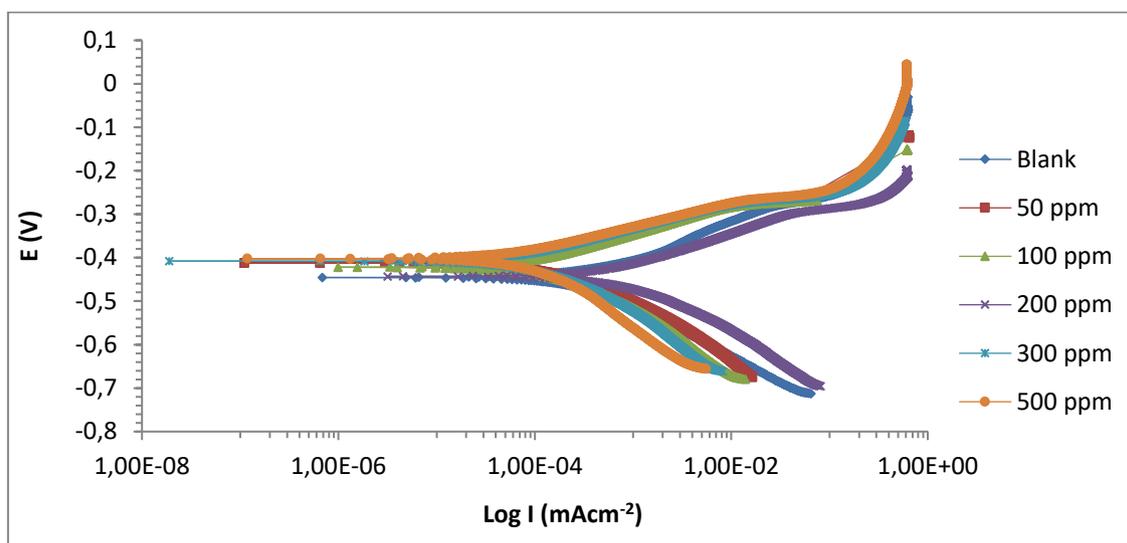

**Figure 1.** Potentiodynamic Polarization curve for a carbon steel in 2 M HCl in the absence and presence of different concentrations of Levofloxacin at 303 K.

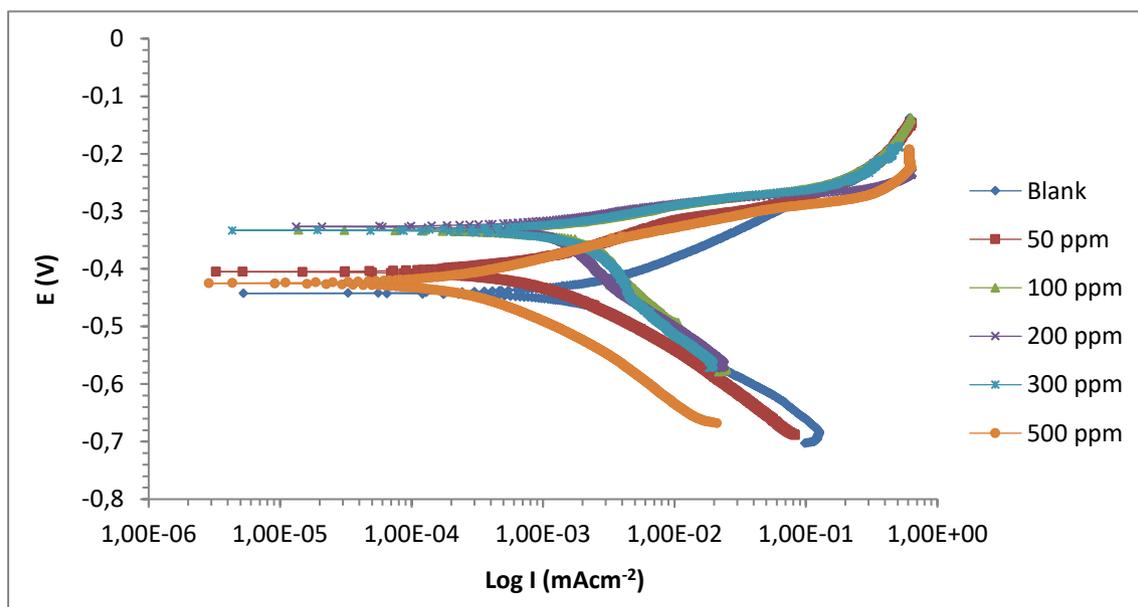

**Figure 2.** Potentiodynamic Polarization curve for a carbon steel in 2 M HCl in the absence and presence of different concentrations of Levofloxacin at 323 K.

Polarization plots for carbon steel in 2 M HCl solution in absence and presence of dissimilar concentrations of (Blank, 50 ppm, 100 ppm, 200 ppm, 300 ppm and 500 ppm) of Levofloxacin are made known in **Figure 1** and **Figure 2**. From the curves it can be seen that the cathodic and anodic branches of the Tafel polarization curves are shifted towards lower current to similar extent in the presence of Levofloxacin, which may be as a result of the blocking effect of the adsorbed inhibitor molecules. It can also be deduced from the plots that the studied inhibitor inhibits corrosion by controlling both cathodic and anodic reactions (mixed type inhibitor), since the anodic and cathodic reactions are affected by Levofloxacin. This implies that the addition of inhibitor reduces anodic dissolution of carbon steel and also retards the cathodic reaction. Electrochemical parameters deduced from the polarization curve are listed in **Table 1**. From the results obtained it can be seen that by increasing the concentration of inhibitor, the corrosion current  $I_{corr}$  is decreased, and inhibition efficiency  $IE\%$  and polarization resistant increase, suggesting that the inhibitor acted by simply blocking the available surface area (Ameh *et al.*, 2016).

**Table 1.** Electrochemical Parameters Obtained from Potentiodynamic Polarization curve.

Inhibitors	Conc., ppm	ba Vdec <sup>-1</sup>	bcVdec <sup>-1</sup>	E <sub>corr</sub> (V)	I <sub>corr</sub> (μAcm <sup>-2</sup> )	CR (mpy)	R <sub>p</sub> (Ωcm <sup>2</sup> )	θ	IE%
	Blank	102	454	-446	560	256	10633		
	50	72	84	-412	98	45	22357	0.8255	82.55
LEVO	100	71	84	-422	92	42	23137	0.8358	83.58
303 K	200	71	79	-417	80	37	24053	0.8573	85.73
	300	64	90	-408	71	32	29029	0.8733	87.33
	500	61	111	-402	65	30	41503	0.8835	88.35
	Blank	116	217	-442	3560	1626	5433		
	50	76	391	-333	3370	1539	9469	0.311	31.10
LEVO	100	61	249	-333	2040	929	5284	0.427	42.28
323K	200	53	541	-326	1770	808	22229	0.503	50.28
	300	74	100	-405	622	284	4752	0.825	82.52
	500	56	87	-425	188	86	8524	0.947	94.71

### 3. 1. 1. Effect of Temperature

Examination of temperature dependence of inhibition efficiency as well as comparison of corrosion activation energies in absence and presence of inhibitor give some insight into the possible means of inhibitor adsorption (Okafor *et al.*, 2010). Increase in inhibition efficiency with the increase in temperature, with corresponding decrease in corrosion

activation energy in the presence of inhibitor compared to its absence is often interpreted as being indicative of the formation of chemical adsorption layer, while a decline in inhibition efficiency with ascend in temperature, with a corresponding increase in corrosion activation energy in the presence of inhibitor compared to its absence, is attributed to physical adsorption mechanism (Okafor *et al.*, 2010; Fouda *et al.*, 2016). The trend in inhibition efficiency with temperature obtained are listed in Table 1, suggesting chemical adsorption of the inhibitor on the metal surface. The apparent activation energies  $E_a$ , for the dissolution of carbon steel in 2 M HCl in the absence and presence of the inhibitor, were calculated from condensed Arrhenius equation:

$$\log \frac{CR_2}{CR_1} = \frac{E_a}{2.303R} \left( \frac{1}{T_1} - \frac{1}{T_2} \right) \quad 2$$

where:  $CR_1$  and  $CR_2$  are the corrosion rates at temperature  $T_1$  and  $T_2$ , respectively. The calculated activation energy values are shown in **Table 2**. The results indicated that  $E_a$  in the presence of the inhibitor is not consistent. This behaviour is an indication of Physical and Chemical adsorption of the studied inhibitor on the metal surface. The evaluation of heat of adsorption  $Q_{ads}$  was Obtained from the trend of surface coverage with temperature as follows:

$$Q_{ads} = 2.303R \left[ \log \left( \frac{\theta_2}{1-\theta_2} \right) - \log \left( \frac{\theta_1}{1-\theta_1} \right) \right] \times \left( \frac{T_1 \times T_2}{T_2 - T_1} \right) \quad 3$$

where:  $\theta_1$  and  $\theta_2$  are the degrees of surface coverage at temperatures  $T_1$  and  $T_2$ , respectively; the estimated values of heat of adsorption are listed in Table 2. The negative values are consistent with inhibitor with a physical adsorption (Fouda *et al.*, 2016).

**Table 2.** Calculated values of Activation energy  $E_a$  and Heat of adsorption  $Q_{ads}$


Conc., ppm	$E_a$ , kJ/mol	$Q_{ads}$ , kJ/mol	$\theta_1$	$\theta_2$
Blank	73.33175			
50	140.7051	-57.71	0.8255	0.053
100	122.5659	-78.11	0.8358	0.427
200	123.1439	-72.53	0.8573	0.503
300	86.41877	-15.34	0.8733	0.825
500	43.02858	-35.07	0.8835	0.947

### 3. 1. 2. Adsorption Isotherm

The possible ways of discussing the mechanism of corrosion inhibition are by adsorption of organic compounds which block the metal surface and thus reduce the corrosion process. The adsorption provides the information about the interaction among the adsorbed molecules themselves, as well their interaction with the metal surface. Adsorption isotherms are very important to understand the mechanism of heterogeneous organic electrochemical reaction involving solid surfaces. The experimental data were applied to different adsorption

isotherm equations. It was found that the experimental data fitted the Langmuir adsorption isotherm, as shown in **Figure 3**, which may be formulated as:

$$\log \frac{C}{\theta} = \log C + \log K_{ads} \quad 4$$

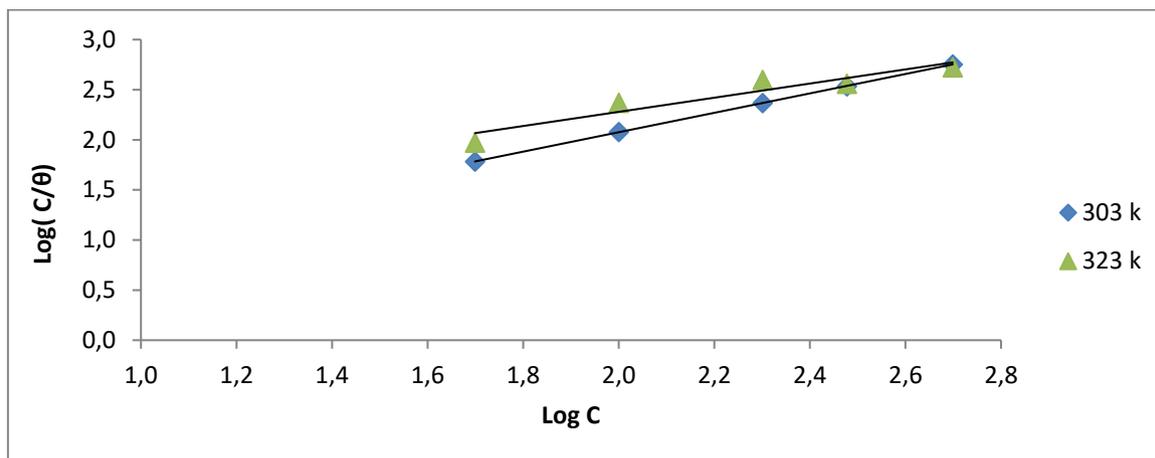

**Figure 3.** Langmuir adsorption isotherm plot for the adsorption of the Levofloxacin on a carbon steel in 2 M HCl.

This plots are linear with the slope and correlation coefficients ( $R^2$ ) near unity. The thermodynamic adsorption parameter ( $\Delta G_{ads}$ ) was calculated from the eq. 5 at different temperatures, and listed in **Table 3**.

$$\Delta G_{ads} = -2.303 RT \log 55.5 K_{ads} \quad 5$$

where 55.5 is the concentration of water in  $\text{mol}\cdot\text{L}^{-1}$ ,  $R$  is the gas constant,  $T$  is the absolute temperature,  $K_{ads}$  is equilibrium constant, and  $\Delta G_{ads}$  is the free energy of adsorption.

**Table 3.** Calculated value of free energy of adsorption.


Temp., K	$K_{ads}$	Slope	$\Delta G_{ads}$	$R^2$
303	0.138	0.968	-10.92	0.999
323	0.866	0.899	-16.14	0.899

The negative sign of free energy ( $\Delta G_{ads}$ ) in Table 3 indicates that the adsorption of the study compounds on the surface of the API 5L X-52 steel was spontaneous. It is well known from the study of adsorption that the values of  $\Delta G_{ads}$  ranging from  $-40 \text{ kJ}\cdot\text{mol}^{-1}$  and given above reflect chemisorptions which involve charge sharing or transfer from the inhibitor


molecules to metal surface to form coordinated bond type, whereas those below  $-40 \text{ kJ}\cdot\text{mol}^{-1}$  to  $1 \text{ kJ}\cdot\text{mol}^{-1}$  signify electrostatic interaction between metal surface and charge organic molecules in the bulk of the solution, identifying a physisorption (Fouda *et al.*, 2016). Therefore the calculated  $\Delta G_{\text{ads}}$  values, between  $10 - 16 \text{ kJ}\cdot\text{mol}^{-1}$  indicate that the adsorption mechanism of the studied molecules on API 5L X-52 steel in 2 M HCl solution is the physisorption.

### 3. 2. Quantum Chemical Calculations


Quantum chemical calculations were carried out in order to investigate the adsorption and inhibition mechanism of the studied compound (Bhawsar *et al.*, 2015). **Fig. 4** shows complete geometric optimization of the studied inhibitor. The HOMO and LUMO (frontier molecular Orbital ) present in the Levofloxacin compound are shown in **Fig. 5**.

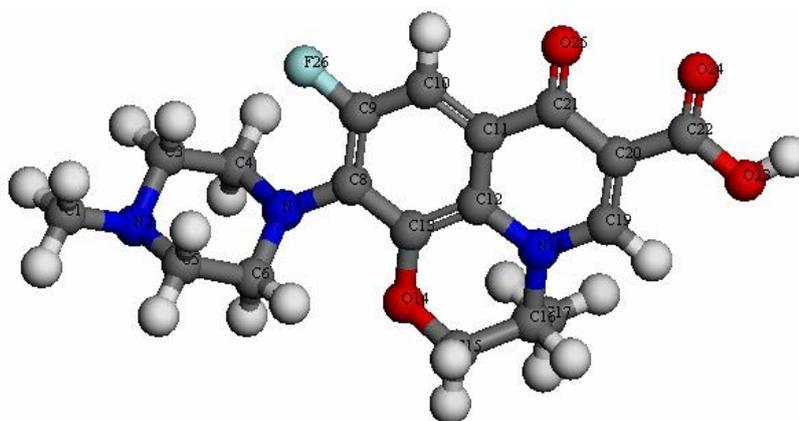

**Figure 4.** Optimized structure of the studied molecule Levofloxacin.

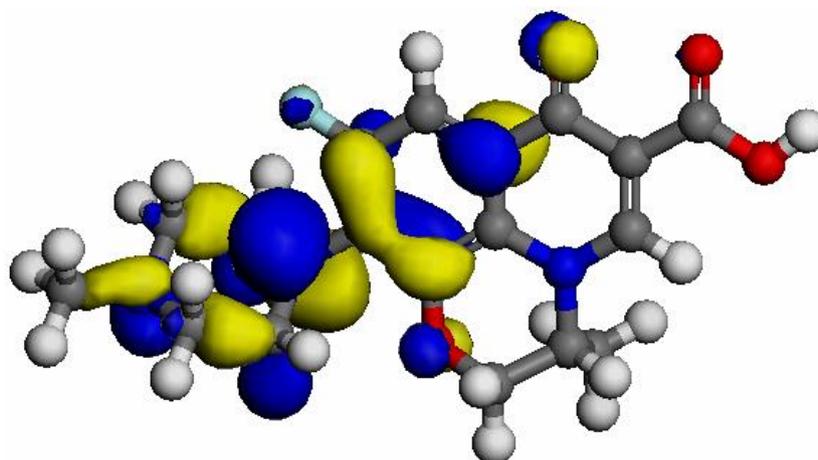

HOMO

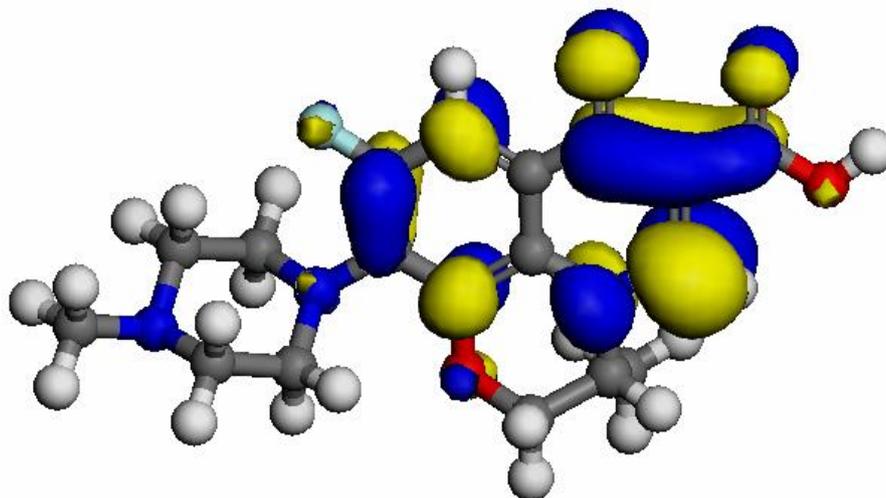

LUMO


**Figure 5.** Schematic Representation of the HOMO and LUMO of molecular Orbital structure of Levofloxacin.

In order to understand the nature of the interaction of the compound with the metal surface one should focus on the composite index that directly control the electronic interaction of the inhibitor molecules with the metal surface. The indexes include:  $E_{\text{HOMO}}$ ,  $E_{\text{LUMO}}$ ,  $\Delta E$  and dipole moment  $\mu$ , etc. listed in **Table 4** (Bhawsar *et al.*, 2015).

**Table 4.** Calculated Quantum Parameters for levofloxacin.

$E_{\text{HOMO}}$ (eV)	$E_{\text{LUMO}}$ (eV)	$\Delta E$ (eV)	$M$ (debyes)
-4708	-2.204	2.504	8.955

$E_{\text{HOMO}}$  is often connected with the electron donating ability of a molecule, higher energy value of  $E_{\text{HOMO}}$  reveals the ability of the molecule to donate electron to an empty molecular orbital. Thus the increase in  $E_{\text{HOMO}}$  value facilitates adsorption or inhibition. Therefore the energy of LUMO shows the capability of the molecule to accept electrons, the lower the value of  $E_{\text{LUMO}}$  the more likely the molecule accepts electrons. The lower the value of energy gap ( $\Delta E$ ), the higher the inhibition efficiency, because the energy to remove an electron from the last occupied orbital will be low; and the higher value of dipole moment ( $\mu$ ) favours accumulation of the inhibitor on the surface layer (Bahwsar *et al.*, 2015; Kumar *et al.*, 2016). The adsorption of the inhibitor on the steel (Fe) surface takes place nearly parallel to the surface so as to maximize its contact with the surface, as shown in **Figure 6**.

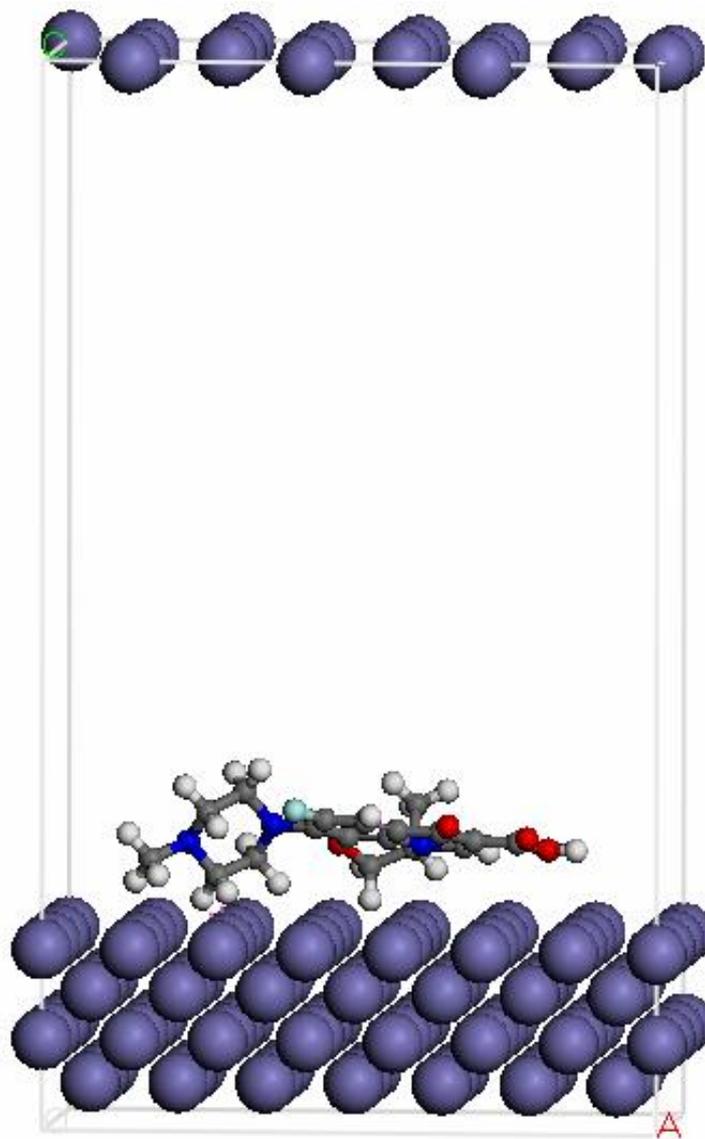

**Figure 6.** The adsorption of the inhibitor on the steel/Fe surface.

#### **4. CONCLUSIONS**

Levofloxacin compound was tested for the corrosion inhibition process on a carbon steel in 2 M HCl solution, using Potentiodynamic polarization and Quantum chemical calculations. The following conclusions can be drawn from the study.

- (1) The inhibition efficiency of the studied compound increases with increasing concentrations
- (2) The adsorption behaviour of levofloxacin on carbon steel in 2 M HCl obeys Langmuir isotherm and involves physical and chemical adsorption mechanism
- (3) Levofloxacin is a good corrosion inhibitor and acts as mixed type

- (4) Quantum chemical parameters, such as  $E_{\text{HOMO}}$ ,  $E_{\text{LUMO}}$ , energy gap and dipole moment suggest that levofloxacin has higher corrosion inhibition strength.

## References

- [1] Abdullatef, O.A. (2015). Chemical and Electrochemical Studies on the corrosion of mild steel, copper and Zinc in 0.5 M  $\text{H}_2\text{SO}_4$  Solution in presence of Azithromycin as effective corrosion inhibitor. *Journal of Advances in Chemistry*, 11 (6), 3642- 3655.
- [2] Akpan, I.A. & Offiong, N.O. (2014a). Electrochemical study of the corrosion of mild steel in hydrochloric acid by Amlodipine Drugs. *International Journal of Chemistry and Materials Research*, 2 (3), 23-29.
- [3] Akpan, I.A. & Offiong, N.O. (2014b). Electrochemical investigation of the inhibitory action of Ciprofloxacin Drugs on the acid corrosion of mild steel. *Chemical and Process Engineering Research*, 26, 20-23.
- [4] Ameh, P.O., Ukoha, P., Ejikeme, P. & Eddy N.O. (2016). Thermodynamic, chemical and Electrochemical investigation of 4-hydrobenzoic acid as corrosion inhibitor for mild steel corrosion in hydrochloric acid solution. *Industrial Chemistry*, 2(2), 2469-9764.
- [5] Bhawsar, J., Jain, P.K. and Jain, P. (2015). Experimental and Computational Studies of Nicotiana tabacum leaves extract as green corrosion inhibitor for mild steel in acidic medium. *Alexandria Engineering Journal* 54 (2015) 769-775.
- [6] A.S. Fouda, F.Sh. Mohamed, M.W. El-Sherbeni (2016). Corrosion Inhibition of Aluminum-Silicon Alloy in Hydrochloric Acid Solutions Using Carbamide Thioanhydride Derivatives. *Journal of Bio and Tribo-Corrosion*, 2, 11. doi:10.1007/s40735-016-0039-y
- [7] Kumar, S., Vashisht, H., Olasunkanmi, L.O., Bahadur, I., Verma, H., Singh, G., Obot, I.B. and Ebenso, E.E. (2016). Experimental and Theoretical studies on the inhibition of mild steel corrosion by some synthesized polyurethane tri-block co-polymers. *Scientific Reports*, 6, 30937. doi:101038/srep30937.
- [8] Naqvi, I., Saleemi, A.R. and Naveed, S.(2011). Cefixime: A drug as efficient corrosion inhibitor for mild steel in acidic media. Electrochemical thermodynamic studies. *International Journal of Electrochemical Science*, 6 (2011), 146-161
- [9] Okafor, P.C., Ebenso, E.E. & Ekpe, U.J. (2010). Azadirachta indica extracts as corrosion inhibitor for mild steel in acid medium. *International Journal of Electrochemical Science*, 5, 978-993.
- [10] Siaka, A.A., Eddy, N.O., Idris, S.O., Magaji, L., Garba, Z.N. & Shabanda, I.S. (2013). Quantum Chemical Studies of corrosion inhibition and adsorption potentials of Amoxicillin on mild steel in HCl solution. *International Journal of Modern Chemistry*, 4(1), 1-10.

- [11] Krzysztof Rokosz, Tadeusz Hryniewicz, Stanisław Trzeszczkowski, Comparative Corrosion Study of Austenitic AISI 304L and 316Ti Stainless Steels in the Ammonium nitrate/Urea Solution (AUS). *World Scientific News* 49(2) (2016) 249-271
- [12] Krzysztof Rokosz, Tadeusz Hryniewicz, Michał Uran. A Study of Corrosion Behavior of Austenitic AISI 304L and 316Ti Stainless Steels in the Animal Slurry. *World Scientific News* 50 (2016) 174-185
- [13] Xue Hui Pang, Wen Juan Guo, Wei Hua Li, Jian Dong Xie, Bao Rong Hou. Electrochemical, quantum chemical and SEM investigation of the inhibiting effect and mechanism of ciprofloxacin, norfloxacin and ofloxacin on the corrosion for mild steel in hydrochloric acid. *Science in China Series B: Chemistry* October 2008, Volume 51, Issue 10, pp 928–936
- [14] Sykes J.M. 25 years of progress in electrochemical methods. *Br Corros J*, 1990, 25(4): 175–183
- [15] Sinko J. Challenges of chromate inhibitor pigments replacement in organic coatings. *Prog Org Coat*, 2001, 42(3–4): 267–282
- [16] Sekine I., Nakahata Y., Tanabe H. The corrosion inhibition of mild steel by ascorbic and folic acids. *Corros Sci*, 1988, 28(10): 987–1001
- [17] Bendahou M., Benabdellah M., Hammouti B. A study of rosemary oil as a green corrosion inhibitor for steel in 2 M H<sub>3</sub> PO<sub>4</sub>. *Pig Res Tech*, 2006, 35(2): 95–100
- [18] Moretti G., Guidi F., Grion G. Tryptamine as a green iron corrosion inhibitor in 0.5 M deaerated sulphuric acid. *Corros Sci*, 2004, 46(2): 387–403
- [19] Bethencourt M, Botana F.J., Calvino J.J., Marcos M., Rodríguez-Chacón M.A. Lanthanide compounds as environmentally friendly corrosion inhibitors of aluminium alloys: A review. *Corros Sci*, 1998, 40(11): 1803–1819
- [20] Pandian B.R., Mathur G.S. Inhibitive effect of black pepper extract on the sulphuric acid corrosion of mild steel. *Mater Lett*, 2008, 62(17–18): 2977–2979
- [21] El-Etre A.Y. Inhibition of aluminum corrosion using *Opuntia* extract. *Corros Sci*, 2003, 45(11): 2485–2495
- [22] Lebrini M., Lagrenée M., Vezin H., Gengembre L., Bentiss F. Electrochemical and quantum chemical studies of new thiadiazole derivatives adsorption on mild steel in normal hydrochloric acid medium. *Corros Sci*, 2005, 47(2): 485–505
- [23] Hosseini M., Mertens S.F.L., Ghorbani M., Arshadi M.R. Asymmetrical Schiff bases as inhibitors of mild steel corrosion in sulphuric acid media. *Mater Chem Phys*, 2003, 78(3): 800–808

( Received 05 March 2017; accepted 17 March 2017 )